

**ISSN 2518-170X (Online),  
ISSN 2224-5278 (Print)**

ҚАЗАҚСТАН РЕСПУБЛИКАСЫ  
ҰЛТТЫҚ ФЫЛЫМ АКАДЕМИЯСЫ

Satbayev University

# **ХАБАРЛАРЫ**

---

## **ИЗВЕСТИЯ**

НАЦИОНАЛЬНОЙ АКАДЕМИИ  
НАУК РЕСПУБЛИКИ  
КАЗАХСТАН  
Satbayev University

## **NEWS**

OF THE ACADEMY OF SCIENCES  
OF THE REPUBLIC OF  
KAZAKHSTAN  
Satbayev University

**SERIES**  
**OF GEOLOGY AND TECHNICAL SCIENCES**

**3 (453)**

**MAY – JUNE 2022**

THE JOURNAL WAS FOUNDED IN 1940

PUBLISHED 6 TIMES A YEAR

ALMATY, NAS RK

---

*NAS RK is pleased to announce that News of NAS RK. Series of geology and technical sciences scientific journal has been accepted for indexing in the Emerging Sources Citation Index, a new edition of Web of Science. Content in this index is under consideration by Clarivate Analytics to be accepted in the Science Citation Index Expanded, the Social Sciences Citation Index, and the Arts & Humanities Citation Index. The quality and depth of content Web of Science offers to researchers, authors, publishers, and institutions sets it apart from other research databases. The inclusion of News of NAS RK. Series of geology and technical sciences in the Emerging Sources Citation Index demonstrates our dedication to providing the most relevant and influential content of geology and engineering sciences to our community.*

Қазақстан Республикасы Үлттық ғылым академиясы «ҚР ҰFA Хабарлары. Геология және техникалық ғылымдар сериясы» ғылыми журналының Web of Science-тің жаңаланған нұсқасы Emerging Sources Citation Index-те индекстелуге қабылданғанын хабарлайды. Бұл индекстегі барысында Clarivate Analytics компаниясы журналды одан әрі the Science Citation Index Expanded, the Social Sciences Citation Index және the Arts & Humanities Citation Index-ке қабылдау мәселесін қарастыруды. Web of Science зерттеушілер, авторлар, баспашилар мен мекемелерге контент тереңдігі мен сапасын ұсынады. ҚР ҰFA Хабарлары. Геология және техникалық ғылымдар сериясы Emerging Sources Citation Index-ке енүі біздің қоғамдастық үшін ең өзекті және беделді геология және техникалық ғылымдар бойынша контентке адалдығымызды білдіреді.

НАН РК сообщает, что научный журнал «Известия НАН РК. Серия геологии и технических наук» был принят для индексирования в Emerging Sources Citation Index, обновленной версии Web of Science. Содержание в этом индексировании находится в стадии рассмотрения компанией Clarivate Analytics для дальнейшего принятия журнала в the Science Citation Index Expanded, the Social Sciences Citation Index и the Arts & Humanities Citation Index. Web of Science предлагает качество и глубину контента для исследователей, авторов, издателей и учреждений. Включение Известия НАН РК. Серия геологии и технических наук в Emerging Sources Citation Index демонстрирует нашу приверженность к наиболее актуальному и влиятельному контенту по геологии и техническим наукам для нашего сообщества.

### **Бас редактор**

**ЖҰРЫНОВ Мұрат Жұрынұлы**, химия ғылымдарының докторы, профессор, КР ҰҒА академигі, Қазақстан Республикасы Үлттық Ғылым академиясының президенті, АҚ «Д.В. Сокольский атындағы отын, катализ және электрохимия институтының» бас директоры (Алматы, Қазақстан) **H = 4**

### **Ғылыми хатшы**

**АБСАДЫКОВ Бахыт Нарикбайұлы**, техника ғылымдарының докторы, профессор, КР ҰҒА жауапты хатшысы, А.Б. Бектұров атындағы химия ғылымдары институты (Алматы, Қазақстан) **H = 5**

### **Редакциялық алқа:**

**ӘБСАМЕТОВ Мәліс Құдысұлы** (бас редактордың орынбасары), геология-минералогия ғылымдарының докторы, профессор, КР ҰҒА академигі, «У.М. Ахмедсафина атындағы гидрогеология және геоэкология институтының» директоры (Алматы, Қазақстан) **H = 2**

**ЖОЛТАЕВ Герой Жолтайұлы** (бас редактордың орынбасары), геология-минералогия ғылымдарының докторы, профессор, К.И. Сатпаев тындағы геология ғылымдары институтының директоры (Алматы, Қазақстан) **H=2**

**СНОУ Дэниел, Ph.D.**, қауымдастырылған профессор, Небраска университетінің Су ғылымдары зертханасының директоры (Небраска штаты, АҚШ) **H = 32**

**ЗЕЛЬТМАН Реймар, Ph.D.**, табиғи тарих мұражайының Жер туралы ғылымдар бөлімінде петрология және пайдалы қазбалар кен орындары саласындағы зерттеулердің жетекшісі (Лондон, Англия) **H = 37**

**ПАНФИЛОВ Михаил Борисович**, техника ғылымдарының докторы, Нанси университетінің профессоры (Нанси, Франция) **H=15**

**ШЕН Пин, Ph.D.**, Қытай геологиялық қоғамының тау геологиясы комитеті директорының орынбасары, Американдық экономикалық геологтар қауымдастырының мүшесі (Пекин, Қытай) **H = 25**

**ФИШЕР Аксель, Ph.D.**, Дрезден техникалық университетінің қауымдастырылған профессоры (Дрезден, Берлин) **H = 6**

**КОНТОРОВИЧ Алексей Эмильевич**, геология-минералогия ғылымдарының докторы, профессор, РГА академигі, А.А. Трофимука атындағы мұнай-газ геологиясы және геофизика институты (Новосибирск, Ресей) **H = 19**

**АГАБЕКОВ Владимир Енокович**, химия ғылымдарының докторы, Беларусь ҰҒА академигі, Жана материалдар химиясы институтының құрметті директоры (Минск, Беларусь) **H = 13**

**КАТАЛИН Стефан**, Ph.D., Дрезден техникалық университетінің қауымдастырылған профессоры (Дрезден, Берлин) **H = 20**

**СЕЙТМУРАТОВА Элеонора Юсуповна**, геология-минералогия ғылымдарының докторы, профессор, КР ҰҒА корреспондент-мүшесі, К.И. Сатпаев атындағы Геология ғылымдары институты зертханасының ментерушісі (Алматы, Қазақстан) **H=11**

**САҒЫНТАЕВ Жанай**, Ph.D., қауымдастырылған профессор, Назарбаев университеті (Нұр-Сұлтан, Қазақстан) **H = 11**

**ФРАТТИНИ Паоло**, Ph.D., Бикокк Милан университеті қауымдастырылған профессоры (Милан, Италия) **H = 28**

---

**«КР ҰҒА Хабарлары. Геология және техникалық ғылымдар сериясы».**

**ISSN 2518-170X (Online)**,

**ISSN 2224-5278 (Print)**

Меншіктеуші: «Қазақстан Республикасының Үлттық ғылым академиясы» РКБ (Алматы қ.). Қазақстан Республикасының Ақпарат және қоғамдық даму министрлігінің Ақпарат комитетінде 29.07.2020 ж. берілген № KZ39VPY00025420 мерзімдік басылым тіркеуіне койылу туралы куәлік. Такырыптық бағыты: *геология, мұнай және газды өндегудің химиялық технологиялары, мұнай химиясы, металдарды алу және олардың қосындыларының технологиясы*.

Мерзімділігі: жылына 6 рет.

Тиражы: 300 дана.

Редакцияның мекен-жайы: 050010, Алматы қ., Шевченко көш., 28, 219 бөл., тел.: 272-13-19

<http://www.geolog-technical.kz/index.php/en/>

© Қазақстан Республикасының Үлттық ғылым академиясы, 2022

---

Типографияның мекен-жайы: «Аруна» ЖК, Алматы қ., Мұратбаев көш., 75.

### **Главный редактор**

**ЖУРИНОВ Мурат Журинович**, доктор химических наук, профессор, академик НАН РК, президент Национальной академии наук Республики Казахстан, генеральный директор АО «Институт топлива, катализа и электрохимии им. Д.В. Сокольского» (Алматы, Казахстан) **H = 4**

### **Ученый секретарь**

**АБСАДЫКОВ Бахыт Нарикбаевич**, доктор технических наук, профессор, ответственный секретарь НАН РК, Институт химических наук им. А.Б. Бектурова (Алматы, Казахстан) **H = 5**

### **Редакционная коллегия:**

**АБСАМЕТОВ Малис Кудысович**, (заместитель главного редактора), доктор геологоминералогических наук, профессор, академик НАН РК, директор Института гидрогеологии и геэкологии им. У.М. Ахмедсафина (Алматы, Казахстан) **H = 2**

**ЖОЛТАЕВ Герой Жолтаевич**, (заместитель главного редактора), доктор геологоминералогических наук, профессор, директор Института геологических наук им. К.И. Сатпаева (Алматы, Казахстан) **H=2**

**СНОУ Дэниел**, Ph.D, ассоциированный профессор, директор Лаборатории водных наук университета Небраски (штат Небраска, США) **H = 32**

**ЗЕЛЬТМАН Реймар**, Ph.D, руководитель исследований в области петрологии и месторождений полезных ископаемых в Отделе наук о Земле Музея естественной истории (Лондон, Англия) **H = 37**

**ПАНФИЛОВ Михаил Борисович**, доктор технических наук, профессор Университета Нанси (Нанси, Франция) **H=15**

**ШЕНПИН**, Ph.D, заместитель директора Комитета по горной геологии Китайского геологического общества, член Американской ассоциации экономических геологов (Пекин, Китай) **H = 25**

**ФИШЕР Аксель**, ассоциированный профессор, Ph.D, технический университет Дрезден (Дрезден, Берлин) **H = 6**

**КОНТОРОВИЧ Алексей Эмильевич**, доктор геолого-минералогических наук, профессор, академик РАН, Институт нефтегазовой геологии и геофизики им. А.А. Трофимука СО РАН (Новосибирск, Россия) **H = 19**

**АГАБЕКОВ Владимир Енокович**, доктор химических наук, академик НАН Беларуси, почетный директор Института химии новых материалов (Минск, Беларусь) **H = 13**

**КАТАЛИН Стефан**, Ph.D, ассоциированный профессор, Технический университет (Дрезден, Берлин) **H = 20**

**СЕЙТМУРАТОВА Элеонора Юсуповна**, доктор геолого-минералогических наук, профессор, член-корреспондент НАН РК, заведующая лаборатории Института геологических наук им. К.И. Сатпаева (Алматы, Казахстан) **H=11**

**САГИНТАЕВ Жанай**, Ph.D, ассоциированный профессор, Назарбаев университет (Нурсултан, Казахстан) **H = 11**

**ФРАТТИНИ Паоло**, Ph.D, ассоциированный профессор, Миланский университет Бикокк (Милан, Италия) **H = 28**

---

**«Известия НАН РК. Серия геологии и технических наук».**

**ISSN 2518-170X (Online)**,

**ISSN 2224-5278 (Print)**

Собственник: Республикаансое общественное объединение «Национальная академия наук Республики Казахстан» (г. Алматы).

Свидетельство о постановке на учет периодического печатного издания в Комитете информации Министерства информации и общественного развития Республики Казахстан № KZ39VPY00025420, выданное 29.07.2020 г.

Тематическая направленность: *геология, химические технологии переработки нефти и газа, нефтехимия, технологии извлечения металлов и их соединений.*

Периодичность: 6 раз в год.

Тираж: 300 экземпляров.

Адрес редакции: 050010, г. Алматы, ул. Шевченко, 28, оф. 219, тел.: 272-13-19

<http://www.geolog-technical.kz/index.php/en/>

© Национальная академия наук Республики Казахстан, 2022

Адрес типографии: ИП «Аруна», г. Алматы, ул. Муратбая, 75.

### **Editorial chief**

**ZHURINOV Murat Zhurinovich**, doctor of chemistry, professor, academician of NAS RK, president of the National Academy of Sciences of the Republic of Kazakhstan, general director of JSC "Institute of fuel, catalysis and electrochemistry named after D.V. Sokolsky" (Almaty, Kazakhstan) **H = 4**

### **Scientific secretary**

**ABSADYKOV Bakhyt Narikbaevich**, doctor of technical sciences, professor, executive secretary of NAS RK, Bekturov Institute of chemical sciences (Almaty, Kazakhstan) **H = 5**

### **E d i t o r i a l b o a r d:**

**ABSAMETOV Malis Kudysovich**, (deputy editor-in-chief), doctor of geological and mineralogical sciences, professor, academician of NAS RK, director of the Akhmedsafin Institute of hydrogeology and hydrophysics (Almaty, Kazakhstan) **H=2**

**ZHOLTAEV Geroy Zholtayevich**, (deputy editor-in-chief), doctor of geological and mineralogical sciences, professor, director of the institute of geological sciences named after K.I. Satpayev (Almaty, Kazakhstan) **H=2**

**SNOW Daniel**, Ph.D, associate professor, director of the laboratory of water sciences, Nebraska University (Nebraska, USA) **H = 32**

**ZELTMAN Reymar**, Ph.D, head of research department in petrology and mineral deposits in the Earth sciences section of the museum of natural history (London, England) **H = 37**

**PANFILOV Mikhail Borisovich**, doctor of technical sciences, professor at the Nancy University (Nancy, France) **H=15**

**SHEN Ping**, Ph.D, deputy director of the Committee for Mining geology of the China geological Society, Fellow of the American association of economic geologists (Beijing, China) **H = 25**

**FISCHERAxel**, Ph.D, associate professor, Dresden University of technology (Dresden, Germany) **H = 6**

**KONTOROVICH Aleksey Emilievich**, doctor of geological and mineralogical sciences, professor, academician of RAS, Trofimuk Institute of petroleum geology and geophysics SB RAS (Novosibirsk, Russia) **H = 19**

**AGABEKOV Vladimir Enokovich**, doctor of chemistry, academician of NAS of Belarus, honorary director of the Institute of chemistry of new materials (Minsk, Belarus) **H = 13**

**KATALIN Stephan**, Ph.D, associate professor, Technical university (Dresden, Berlin) **H = 20**

**SEITMURATOVA Eleonora Yusupovna**, doctor of geological and mineralogical sciences, professor, corresponding member of NAS RK, head of the laboratory of the Institute of geological sciences named after K.I. Satpayev (Almaty, Kazakhstan) **H=11**

**SAGINTAYEV Zhanay**, Ph.D, associate professor, Nazarbayev University (Nursultan, Kazakhstan) **H = 11**

**FRATTINI Paolo**, Ph.D, associate professor, university of Milano-Bicocca (Milan, Italy) **H = 28**

---

**News of the National Academy of Sciences of the Republic of Kazakhstan. Series of geology and technology sciences.**

**ISSN 2518-170X (Online),**

**ISSN 2224-5278 (Print)**

Owner: RPA «National Academy of Sciences of the Republic of Kazakhstan» (Almaty).

The certificate of registration of a periodical printed publication in the Committee of information of the Ministry of Information and Social Development of the Republic of Kazakhstan No. **KZ39VPY00025420**, issued 29.07.2020.

Thematic scope: *geology, chemical technologies for oil and gas processing, petrochemistry, technologies for extracting metals and their connections.*

Periodicity: 6 times a year.

Circulation: 300 copies.

Editorial address: 28, Shevchenko str., of. 219, Almaty, 050010, tel. 272-13-19

<http://www.geolog-technical.kz/index.php/en/>

---

© National Academy of Sciences of the Republic of Kazakhstan, 2022

Address of printing house: ST «Aruna», 75, Muratbayev str, Almaty.

*NEWS of the National Academy of Sciences of the Republic of Kazakhstan*  
**SERIES OF GEOLOGY AND TECHNICAL SCIENCES**

**ISSN 2224-5278**

Volume 3, Number 453 (2022), 265-275  
<https://doi.org/10.32014/2022.2518-170X.195>

UDC 621. 09.1

**K.T. Sherov<sup>1\*</sup>, S.O. Tussupova<sup>2</sup>, A.V. Mazdubay<sup>2</sup>, M.R. Sikhimbayev<sup>3</sup>,  
B.N. Absadykov<sup>4</sup>**

<sup>1</sup>S. Seifullin Kazakh Agro Technical University, Nur-Sultan, Kazakhstan;

<sup>2</sup>Toraigyrov University, Pavlodar, Kazakhstan;

<sup>3</sup>Karaganda Economic University of Kazpotrebsoyuz,  
Karaganda, Kazakhstan;

<sup>4</sup>A.B. Bekturov Institute of Chemical Sciences, Almaty, Kazakhstan.  
E-mail: shkt1965@mail.ru

**INCREASING DURABILITY OF THERMO-FRICTION  
TOOLS BY SURFACING**

**Abstract.** The article presents the results of a study on increasing the wear resistance of the cutting part of thermo-friction tools by surfacing. The main factors that have a prevailing influence on the increase in the consumption of metal-cutting tools in the current conditions of machine-building industries of the Republic of Kazakhstan are revealed.

The analysis of the methods of traditional thermo-frictional treatment and methods of applying coatings to increase the wear resistance of the surface of steels. Analysis of existing surfacing materials showed that STOODY M7-G, STOODY 102-G and OK TUBRODUR 58 O / G M surfacing materials have high hardness, wear resistance and temperature resistance. The technique for studying the hardness of the deposited layers is based on experimental and metallographic research methods. Surfacing of 12 samples of mild structural steel St3 was carried out.

One-layer, two-layer and three-layer surfacing were applied on the surface of the samples. Surfacing of 12 samples of mild structural steel St3 was performed. One-layer, two-layer and three-layer surfacing were applied on the surface of the samples. The results of the study of the hardness of the deposited layers showed that the surfacing materials retain the original hardness during two-layer surfacing. In this case, the thickness of the first and second layers should be 4 and 2 mm, respectively.

**Key words.** Wear resistance, hardness, surfacing material, thermofriction tool, wear, friction, melting point, surfacing.

**К.Т. Шеров<sup>1\*</sup>, С.О. Тусупова<sup>2</sup>, А.В. Маздубай<sup>2</sup>, М.Р. Сихимбаев<sup>3</sup>,  
Б.Н. Абсадыков<sup>4</sup>**

<sup>1</sup>С. Сейфуллин атындағы Қазақ агротехникалық университеті,  
Нұр-Сұлтан, Қазақстан;

<sup>2</sup>Торайғыров университеті, Павлодар, Қазақстан;

<sup>3</sup>Қазтұтыну одағы Қарағанды экономикалық университеті,  
Қарағанды, Қазақстан;

<sup>4</sup>Ә.Б. Бектұров атындағы химия ғылымдары институты,  
Алматы, Қазақстан.

E-mail: *shkt1965@mail.ru*

## **БАЛҚЫМАЛАУ АРҚЫЛЫ ТЕРМОФРИКЦИЯЛЫҚ ҚҰРАЛДАРДЫҢ ТОЗУҒА ТӨЗІМДІЛІГІН АРТТАРУ**

**Аннотация.** Отандық және шетелдік өндірушілердің жаһандық интеграциясы отандық өнеркәсіпте шетелдік техниканы пайдаланудың артуына әкелді. Осыланысты химиялық құрамы мен механикалық қасиеттері бойынша ерекшеленетін жаңа материалдар өндірістерде көбірек қолданыс табуда. Мұндай материалдарды кескіш құралдармен өңдеу кезіндегі шығынына теріс әсерін тигізеді. Себебі, қолданыстағы анықтамалық-техникалық әдебиет көздерінде кесу режимдерін тағайындау және құралдың кесу бөлігінің материалын таңдау сияқты тиісті ұсыныстардың болмауынан жасалған қателер кесу жиегінің мерзімінен бұрын тозуына немесе бұзылуына әкеледі. Бұл мәселенің шешімі, жаһандық даму жағдайында, жоғары сапа, өнімділік, ресурстарды үнемдеу, қол жетімділік және т.б. сияқты өндіріс талаптарын қанағаттандыратын металл кесетін құралдың конструкциясын және механикалық өңдеу әдісін жарату болуы мүмкін. Осылай өңдеудің бірі импульсті салқыннатуы бар термофрикционлық өңдеу әдісі және құралдың конструкциясы. Термофрикционлық өңдеу әдістерін эксперименттік зерттеу нәтижесінде олардың тозуға төзімділігімен байланысты мәселе бар екендігі анықталды. Бірнеше рет кесу құралымен өтулерден кейін, термофрикционлық құралдардың кесу бөлігінде тозу, жарықтар мен сызаттар байқалды. Бұл жұмыста термофрикционлық құралдардың тозуға төзімділігін арттыру үшін балқымалау процесін зерттеу нәтижелері ұсынылған. Балқымалады жасау үшін электр доғалы дәнекерлеу

әдісі таңдалған, ол кеңінен таралған, атап айтқанда отандық машина жасау кәсіпорындарында кең пайдалануда. Қабаттардың қаттылығын зерттеу әдісі эксперименттік және металлографиялық зерттеу әдістеріне негізделген.

Колданыстағы балқыма материалдарды талдау STOODY M7-G, STOODY 102-G және OK TUBRODUR 58 O/G M жоғары қаттылыққа, тозуға және температуралық төзімділікке ие екенін көрсетті. Зерттеу нәтижелері көрсеткендей, барлық үш материал екі қабатты балқымалау кезінде бастапқы қаттылықты сақтайды. Сонымен қатар, бір қабатты балқыманың ортасынан бастап, екі қабатты балқыманың соңына дейін балқыманың қаттылық мәні өзгөрмейтіні анықталды.

Термофрикционный құралдардың кесу бөлігін балқымалау үшін екі қабатты балқыма жеткілікті екендігі анықталды. Бұл жағдайда бірінші және екінші қабаттардың қалындығы сәйкесінше 4 және 2 мм болуы керек.

**Түйін сөздер:** тозуға төзімділік, қаттылық, балқымалау материалы, термофрикционный құрал, тозу, үйкеліс, балқыту температурасы, балқыма.

**К.Т. Шеров<sup>1\*</sup>, С.О. Тусупова<sup>2</sup>, А.В. Маздубай<sup>2</sup>, М.Р. Сихимбаев<sup>3</sup>,  
Б.Н. Абсадыков<sup>4</sup>**

<sup>1</sup>Казахский агротехнический университет им. С. Сейфуллина,  
Нур-Султан, Казахстан;

<sup>2</sup>Университет Торайғырова, Павлодар, Казахстан;

<sup>3</sup>Карагандинский экономический университет Казпотребсоюза,  
Караганда, Казахстан;

<sup>4</sup>Институт химических наук имени А.Б. Бектурова, Алматы, Казахстан.  
E-mail: shkt1965@mail.ru

## ПОВЫШЕНИЕ ИЗНОСОСТОЙКОСТИ ТЕРМОФРИКЦИОННЫХ ИНСТРУМЕНТОВ ПУТЕМ НАПЛАВКИ

**Аннотация.** Глобальная интеграция отечественных и зарубежных производителей привела к увеличению использования в отечественной промышленности зарубежной техники. В связи с этим в производствах все большее применение находят новые материалы, отличающиеся по химическому составу и механическим свойствам. Механическая обработка таких материалов также отрицательно влияет на расход металорежущих инструментов.

Решением данной проблемы может быть разработка такого способа

механической обработки и конструкции металлорежущего инструмента, которые удовлетворяли бы такие требования производства, как высокое качество, производительность, ресурсосбережение, доступность и др. в условиях глобального развития.

Одним из таких способов механической обработки является термофрикционная обработка с импульсным охлаждением и конструкция инструмента. В результате проведенных экспериментальных исследований термофрикционных способов обработки было выявлено, что существует проблема, связанная с износостойкостью термофрикционных инструментов. После многократного количества резов на режущей части термофрикционных инструментов наблюдались износы, трещины и сколы. В данной работе представлены результаты исследования процесса наплавки термофрикционных инструментов с целью повышения их износостойкости. Для нанесения наплавок был выбран способ электродуговой сварки.

Методика исследования твердости наплавленных слоев основана на экспериментальных и металлографических методах исследования. Анализ существующих наплавочных материалов показал, что наплавочные материалы STOODY M7-G, STOODY 102-G и OK TUBRODUR 58 O/G M обладают высокой твердостью, износостойкостью и температурной стойкостью. Результаты исследования показали, что все три наплавочных материала сохраняют исходную твердость при двухслойной наплавке.

При этом установлено, что начиная с середины однослойной наплавки до конца двухслойной наплавки значение твердости наплавки не меняется. Установлено, что для наплавки режущей части термофрикционных инструментов достаточно выполнение двухслойной наплавки. При этом толщина первого и второго слоев должна составлять соответственно 4 и 2 мм.

**Ключевые слова:** износостойкость, твердость, наплавочный материал, термофрикционный инструмент, износ, трение, температура плавления, наплавка.

**Introduction.** The efficiency of mechanical engineering production is determined by many factors, among which an important place is taken by metal-cutting tools. Most tool failures (up to 75%) occur due to wear on the cutting edges (Samuel, 2019: 13, Zyuzin, 2019: 3).

This is especially observed when processing difficult-to-process materials, which are widely used in all industries, since for these materials the complexity of processing the workpiece is commensurate with the tool life (Khodzhibergenov, 2019: 4, Makarenko, 2019: 4, Dudak, 2017a: 8). The global integration of domestic and foreign manufacturers has led to an increase in the use of foreign technology in the domestic industry. In this regard, new materials

that differ in chemical composition and mechanical properties are increasingly used in production. The machining of such materials also negatively affects the consumption of metal cutting tools. Since the mistakes made when assigning cutting modes and choosing the material of the cutting part of the tool, due to the lack of relevant recommendations in the available reference and technical sources, lead to premature wear or breakage of the cutting edge.

The situation is further aggravated by the fact that for countries (which include Kazakhstan) that do not have their own tool production, metal cutting tools have to be purchased at a high (overpriced) cost from foreign manufacturers. All this leads to an increase in the cost of mechanical operation, and ultimately an increase in the cost of production. In this regard, the problem of increasing the durability (working life) of the cutting tool during the processing of difficult to process materials is one of the major practical problems of modern engineering. The solution to this problem can be the development of such method of the machining and the design of metal cutting tools that would satisfy such production requirements as high quality, productivity, resource saving, availability, etc. in the context of global development. One of such methods of mechanical processing is thermofriction processing with pulse cooling and tool design (Sherov, 2020a: 9).

As a result of experimental studies of thermofriction segments of metal billets (Sherov, 2017 b: 14), rotational-friction boring of large holes (Kadyrov, 2021: 9, Mukanov, 2019: 4, Zhunusbekova, 2016: 4), it was revealed that there is a problem associated with the wear resistance of thermofriction tools. After a multiple number of cuts on the cutting part of thermofriction tools, wear, cracks and chips were observed. This is the result of a pulse-cooled thermofriction cutting process, where a heating-cooling thermal cycle takes place, which exposes the cutting part of the tool to periodic heat treatment. Studies have been conducted to study the factors affecting the wear of a thermofriction tool, taking into account the cutting mechanism of the processing method, as well as the search for methods and ways to increase its wear resistance. As a result, four areas of scientific research were identified to increase the wear resistance, rigidity and strength of thermofriction cutting tools: Development of a method for selecting the material of a friction cutting disk based on the physical- mechanical properties and chemical composition of the workpiece, Development of manufacturing technology of a cutting disc of friction, contributing to the hardening of the cutting part of the friction disc, Improving the strength characteristics of structural steels (St. 50, St. 65G, etc.) used to manufacture friction discs by improving the chemical composition, Improving the wear resistance of the cutting part of thermofriction tools by surfacing with wear-resistant surfacing materials.

Currently, research is in the fourth direction, increasing the wear resistance of the cutting part of thermofriction tools by surfacing with wear-resistant materials.

**Research materials and methods.** ESAB surfacing materials were selected, which have all the necessary qualities to increase the wear resistance of thermofriction tools and are readily available for machine-building industries in Kazakhstan. For deposition, the method of electric arc welding was chosen, which is also widely distributed, in particular at domestic engineering enterprises. Before surfacing, the surfaces of the samples were preheated to a temperature of  $\approx 150$  °C. Experimentally, surfacing modes were selected. As a result of surfacing, 3 samples were obtained with different layers of deposited material for each type of wire. The first surfacing layer is 4 mm thick, the second and third layers are 2 mm thick. Figure 1 shows the deposited samples.

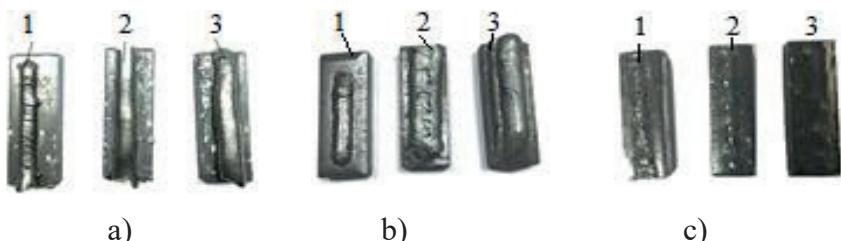


Figure 1. Fused samples: a - surfacing material STOODY M7-G; b - surfacing material STOODY 102-G; c - surfacing material TUBRODUR 58 O / G M; 1 - single-layer surfacing; 2 - two-layer surfacing; 3 - three-layer surfacing

Complying with all standard requirements for organizing and conducting hardness measurements, we carried out the following preparatory work for the study:

1. Samples welded from STOODY M7-G, STOODY 102-G, TUBRODUR 58 O / G M materials were cut transversely into several parts (Fig. 2).

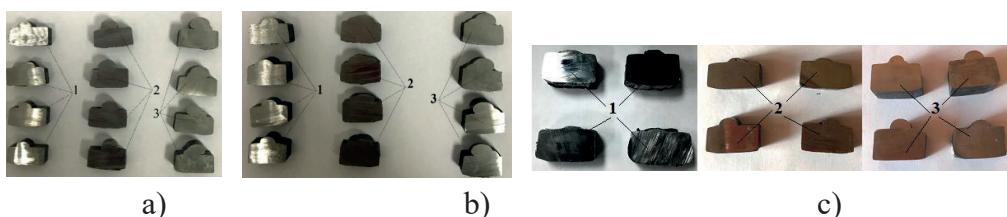


Figure 2. Samples after cutting: a - STOODY M7-G; b - STOODY 102-G; c - TUBRODUR 58 O / G M; 1 - single-layer surfacing; 2 - two-layer surfacing; 3 - three-layer surfacing

The UNITOM-2 cutting machine was used for cutting. The machine is equipped with automatic setting of cutting parameters and an automatic cutting

table for parallel cuts. It has the ability to recirculate cooling (65 l) and perform cutting without deformation and burnout, thanks to the Excicut mode, as well as to illuminate the cutting chamber.

2. It is required to grind the processed parts. For grinding and polishing samples, the automatic machine LABOPOL-5 was used. The grinding process was carried out in four stages: leveling, fine grinding, diamond polishing and oxide polishing. Figure 3 shows the samples after grinding.

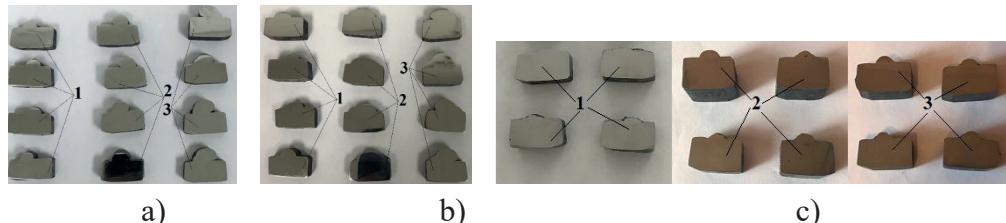


Figure 3. Samples after grinding: a - STOODY M7-G; b - STOODY 102-G; c - TUBRODUR 58 O / G M; 1 - single-layer surfacing; 2- two-layer surfacing; 3 - three-layer surfacing

After grinding, hardness was determined using a WILSON VH1150 hardness tester. The hardness tester is designed to measure the macro-hardness of the material on the Vickers scale. It has a unique range of loads from 300 g to 50 kg (Balgabekov, 2014: 3, Volkov, 2016: 5, Togizbayeva, 2020: 9, Ganyukov, 2018: 12, Dudak, 2019 b: 12). A hardness test was carried out on each prepared sample at 4-5 points. Figure 4 shows diagrams explaining the process of measuring the hardness of samples from surfacing materials STOODY M7-G, STOODY 102-G, TUBRODUR 58 O / G M.

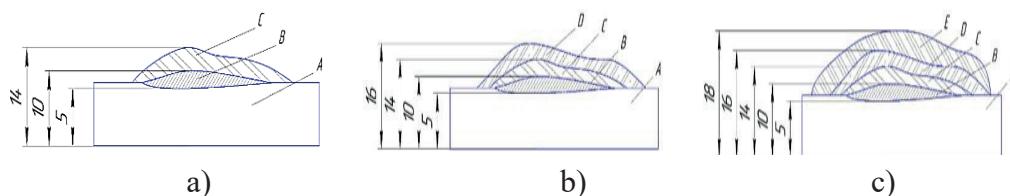


Figure 4. Schemes explaining the process of measuring hardness of samples: a - a sample deposited in one layer; b - a sample deposited in two layers; c - a sample deposited in three layers; A - the main material; B - mixing zone of the material and the surfacing wire; C - the first layer of surfacing; D - the second layer of surfacing; E - the third layer of surfacing

**Results.** After completion of the hardness measurement, the obtained data were processed. According to the results of measuring the hardness of the samples from surfacing materials, STOODY M7-G, STOODY 102-G, TUBRODUR 58 O / G M were built. Figure 5 shows graphs of the distribution of hardness over the deposited layers.

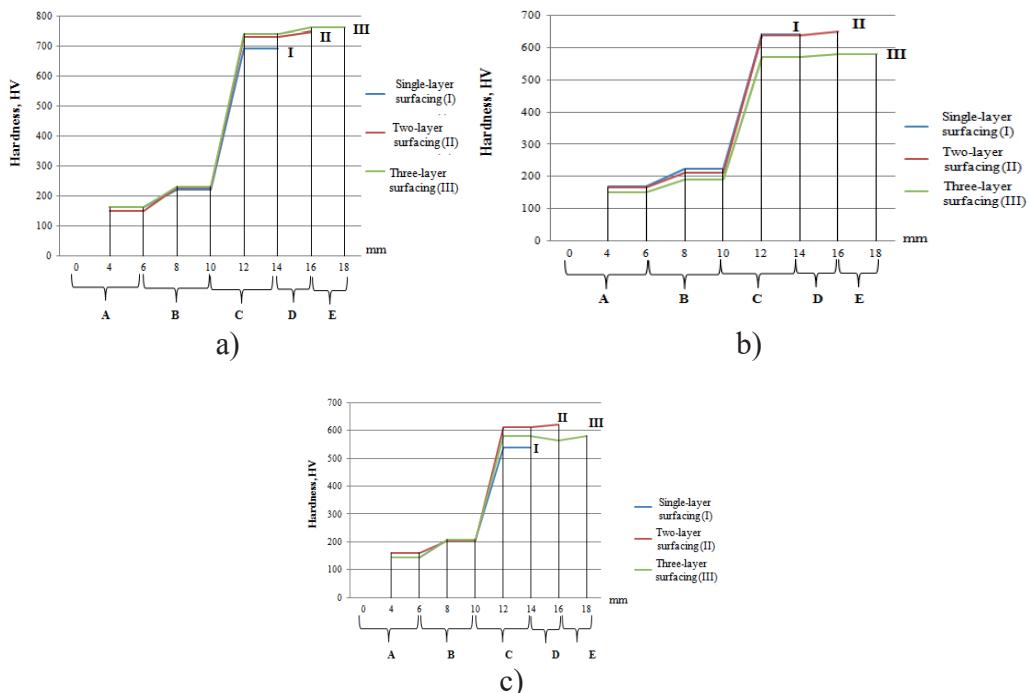


Figure 5. Graphs of the distribution of hardness over the deposited layers of samples: a - STOODY M7-G; b - STOODY 102-G; c - OK TUBRODUR 58; A - the size of the zone of the main material; B - the size of the mixing zone of the material and the surfacing wire; C - the size of the zone of the first layer of surfacing; D - the size of the zone of the second layer of surfacing; E - the size of the zone of the third layer of surfacing

**Discussion.** The results of the study showed that the hardness of the STOODY M7-G surfacing material with three-layer surfacing in BCDE zones is HV 220-760, the hardness of STOODY 102-G surfacing with three-layer surfacing in BCDE zones is HV 222-580, the hardness of TUBRODUR 58 O / GM for three-layer surfacing in BCDE zones is HV 208-580. In all samples deposited from three surfacing materials, there is a decrease in the initial hardness of surfacing materials during single-layer surfacing (zone B, Fig. 5, a, b, c). This is due to the fact that in single-layer surfacing, a decrease in

hardness occurs due to mixing of the surfacing material with the base metal. It can be seen from the graphs that all three surfacing materials retain their original hardness during two-layer surfacing (zone D of Fig. 5, a, b, c). It was found that starting from the middle of a single-layer surfacing (see zone C with a height of 12 mm, Fig. 5 a, b, c) to the end of a two-layer surfacing (zone D with a height of 16 mm, Fig. 5 a, b, c) value of hardness of surfacing does not change. This conclusion makes it possible to abandon the third layer of surfacing. Based on this, it can be recommended for surfacing the cutting part of thermofriction tools in two layers. The thickness of the first and second layers can be set respectively within 4 and 2 mm. Based on the results, according to the above recommendations, pilot batches of thermofriction tools were manufactured. The cutting parts of a circular saw for cutting metal blanks, cup cutters for turning external cylindrical surfaces and boring holes, a friction cutter for thermofriction milling, a conical friction cutter for milling a conical surface were surfaced. Samples for thermofriction treatment were prepared from various materials. The results of the tests showed that the wear resistance of thermofriction tools made with surfacing increased by 1.5-2 times in comparison with tools without surfacing. In the future, the study of quality indicators during thermofriction processing using deposited tools, in particular roughness and stress-strain state of the treated surfaces, as well as the distribution of temperature and hardness during processing, is relevant.

**Conclusions.** The results of the study showed that the absence of tool production in the Republic of Kazakhstan negatively affects the full-scale development of the engineering complex. Tool support focused on the purchase of metal cutting tools from foreign manufacturers leads to an increase in the cost of mechanical operations, and ultimately an increase in the cost of production.

It has been established that the cutting parts of thermofriction tools in the process of thermofriction processing with impulse cooling, where the thermal cycle of heating-cooling occurs, undergoes periodic heat treatment. As a result, after a multiple number of cuts, wear, cracks and chips appear on the cutting part of thermofriction tools. Analysis of existing surfacing materials showed that surfacing materials STOODY M7-G, STOODY 102-G and OK TUBRODUR 58 O / G M have high hardness, wear resistance and temperature resistance.

The results of the study showed that all three surfacing materials retain their original hardness during two-layer surfacing (zone D of Fig. 5, a, b, c). It was found that starting from the middle of a single-layer surfacing (zone C with a height of 12 mm, Fig. 5, a, b, c) to the end of a two-layer surfacing (zone D with a height of 16 mm, Fig. 5, a, b, c), the hardness value surfacing does not change. It was established that for surfacing the cutting part of thermofriction

tools, it is sufficient to perform two-layer surfacing. The thickness of the first and second layers should be 4 and 2 mm, respectively.

Prototypes of thermofriction tools were manufactured and tested. The test results showed an increase in the wear resistance of thermofriction tools by 1.5-2 times. In the future, it is of scientific and practical interest to study the thermal phenomena occurring in the cutting zone and the stress-strain state of the treated surfaces using thermofriction tools with surfacing.

### **Information about the authors:**

**Sherov Karibek Tagayevich** – Doctor of Engineering Sciences, Professor, S. Seifullin Kazakh Agro Technical University, Nur-Sultan, Kazakhstan, E-mail: [shkt1965@mail.ru](mailto:shkt1965@mail.ru), ORCID: <https://orcid.org/0000-0003-0209-180X>;

**Tussupova Sayagul Oralovna** – Dr. PhD, Senior Lecturer, Toraigyrov University, Pavlodar, Kazakhstan, E-mail: [suleeva.s@inbox.ru](mailto:suleeva.s@inbox.ru); ORCID: <https://orcid.org/0000-0002-8920-4901>;

**Mazdubai Asylkhan Vladimirovich** – Dr. PhD, Senior Lecturer, Toraigyrov University, Pavlodar, Kazakhstan, E-mail: [asylkhan\\_m@mail.ru](mailto:asylkhan_m@mail.ru); ORCID: <https://orcid.org/0000-0002-2421-042X>;

**Sikhimbayev Muratbay Ryzdkbayevich** – Doctor of Economic Sciences, Professor, Karaganda economic university of Kazpotrebsoyuz, Karaganda, Kazakhstan; E-mail: [smurat@yandex.ru](mailto:smurat@yandex.ru), ORCID: <https://orcid.org/0000-0002-8763-6145>;

**Absadykov Bakhyt Narikbayevich** – Doctor of Technical Sciences, Professor, the Corresponding member of National Academy of Sciences of the Republic of Kazakhstan, A.B. Bekturov Institute of Chemical Sciences, Almaty, Kazakhstan; E-mail: [b\\_absadykov@mail.ru](mailto:b_absadykov@mail.ru), ORCID: <https://orcid.org/0000-0001-7829-0958>.

### **REFERENCES**

Balgabekov T.K., Issin D.K., Kimanov B.M., Akashev A.Z., Issin B.D. Studying and improving blast furnace cast iron quality, *Metalurgija*, 2014, 53(4), ctp. 556–558. (in Eng.).

Dudak N., Taskarina A., Kasenov A., Itybäeva G., Mussina Z., Abishev K., Mukanov R. (2017) Hole Machining Based on Using an Incisive Built-Up Reamer, International Journal of Precision Engineering and Manufacturing, Volume 18, Issue 10, Pages 1425-1432. <https://doi.org/10.1007/s12541-017-0170-9> (in Eng.).

Dudak N., Itybäeva G., Kasenov A., Mussina Zh., Taskarina A., Abishev K. Multi- ute drill-broach for precision machining of holes, Scientia Iranica, Transactions B: Mechanical Engineering 26 (2019) P.1415-1426. DOI: <https://doi.org/10.24200/sci.2018.5623.1379> (in Eng.).

Ganyukov A.A., Kadyrov A.S., Balabekova K.G., Kurmasheva B.K. (2018) Tests and calculations of structural elements of temporary bridges, Roads and Bridges - Drogi i Mosty 17, P.215 - 226 DOI: 10.7409/rabdimm.018.014 (in Eng.).

Khodzhibergenov D.T., Ibragimova Z.A., Khodzhibergenova U.D. *Abdukarimov A., Esirkepov A.* (2019) Some aspects of software in cutting tools designing and testing, Russian Engineering Research. Vol. 39. pp 772-775. <https://doi.org/10.3103/S1068798X19090090> (in Eng.).

Kadyrov A., Zhunusbekova Zh., Ganyukov A., Kadyrova I., Kukesheva A. General Characteristics for Loading the Working Elements of Drilling and Milling Machines when Moving in the Clay Solution, Communications - Scientific Letters of the University of Zilina. - 2021. - Vol. 23, no. 2. P. B97-B105. DOI: <https://doi.org/10.26552/com.C.2021.2.B97-B105> (in Eng.).

Makarenko K.V., Zabelin A.L., Savinov D.N. (2019) A rational choice of the method for the restoration of parts by the method of manual arc surfacing of a wear-resistant layer [Ratsional'nyy vybor metoda vosstanovleniya detaley metodom ruchnoy dugovoy naplavki iznosostoykogo sloya] Bulletin of the Bryansk State Technical University No. 2 (75). P.12-15. (in Russian).

Mukanov R.B., Kasenov A.Z., Itybaeva G.T., Musina Zh.K., Abishev K., Bykov P.O. (2019) Face Turning of Holes, Russian Engineering Research, Volume 39, Issue 1, Pages 75-78. DOI: 10.3103/S1068798X19010064 (in Eng.).

Sherov K.T., Sakhimbayev M.R., Nasad T.G., Absadykov B.N., Izotova A.S., Okimbayeva A.E., Kuanov I.S. (2020) The research of the steel cutting blade reliability for thermo-frictional processing, News of the National Academy of Sciences of the Republic of Kazakhstan. Series of geology and technical sciences. 2020. Volume 1, Number 439, P.122 – 130. <https://doi.org/10.32014/2020.2518-170X.15> ISSN 2518-170X. (Online), ISSN 2224-5278 (Print). (in Eng.).

Sherov K.T., Sakhimbayev M.R., Donenbayev B.S., Sagitov A.A., Ainabekova S.S. (2017) Experimental Research of Rotational-and-Frictional Boring of Big Holes in Large Parts, Journal of Theoretical and Applied Mechanics, Sofia, Vol. 47, No. 4, P. 23-36. <https://doi.org/10.1515/jtam-2017-0018> (in Eng.).

Togizbayeva B.B., Sazambayeva B.T., Karazhanov A.A., Kenesbek A.B., Cocoşılı M. (2020) Simulation of operation of neural network with purpose of utilisation of hydraulic actuators in complicated technical conditions, *International Journal of Agricultural and Biological Engineering* [this link is disabled](https://link.springer.com/article/10.1007/s40537-020-00312-w), 2020, 13(1), P.11–19. (in Eng.).

Volkov D.I., Proskuryakov S.L., Druzhkov S.S. (2016) The use of modified multifunctional coatings of metal-cutting tools during turning of high-strength cast iron [Ispol'zovaniye modifitsirovannykh mnogofunktional'nykh pokrytiy metallorezhushchikh instrumentov pri tokarnoy obrabotke vysokoprochnogo chuguna] Mechanical Engineering Bulletin - Moscow: LLC Publishing House Innovative Engineering, No. 9. P. 79-83. (in Russian).

Zyuzin A.A., Konstantinova I.S., Kaz'min B.N., Yurov M.D. (2019) Determination of Tool Life in the Cutting of Conical Gears with Circular Teeth. Russian Engineering Research 39, P.396–398. <https://doi.org/10.3103/S1068798X19050228> (in Eng.).

Zhunusbekova Zh.Zh., Kadyrov A.S. (2016) Study of digging machine flat element loading in clay solution, Journal “Naukovyi Visnyk Natsionalnoho Hirnychoho Universytetu” Volume 2 (152), P.30-33. (in Eng.).

## **МАЗМҰНЫ-СОДЕРЖАНИЕ-CONTENTS**

<b>R.A. Abdulvaliyev, M.N. Kvyatkovskaya, L.M. Imangalieva, A.I. Manapova</b>	
KAOLINITE RAW MATERIALS OF KAZAKHSTAN AND THE METHOD OF THEIR BENEFICIATION.....	6
<b>A.E. Abetov, Sh.B. Yessirkepova, J. Curto Ma</b>	
GRAVITY FIELD TRANSFORMS AT THE EXPLORATION FOR HYDROCARBON FIELD IN THE SOUTHERN PART OF THE USTYURT REGION.....	17
<b>E.B. Abikak, B.K. Kenzhaliев</b>	
DEVELOPMENT OF AN INTEGRATED TECHNOLOGY INTENDED TO PROCESS PYRITE SLAG USING CHEMICAL PRE-ACTIVATION.....	32
<b>R.Zh. Abuova, D.K. Suleyev, G.A. Burshukova</b>	
STUDY OF DAMPING PROPERTIES OF ALLOYED STEELS WITH CERAMIC-METALLIC NANOSTRUCTURED COATING FOR CRITICAL PARTS.....	52
<b>N.R. Akhundova</b>	
CHANGE OF HYDRODYNAMIC PRESSURES IN THE WELLBORE OF INCLINED-HORIZONTAL WELLS DURING DRILLING MUD CIRCULATION.....	66
<b>M. Bissengaliev, R. Bayamirova, A. Togasheva, A. Zholbasarova, Zh. Zaydemova</b>	
ANALYSIS OF COMPLICATIONS ASSOCIATED WITH THE PARAFFINIZATION OF BOREHOLE EQUIPMENT AND MEASURES TO PREVENT THEM.....	76
<b>T.I. Espolov, A.G. Rau, N.N. Balgabayev, E.D. Zhaparkulova, Josef Mosiej</b>	
GEOLOGICAL STRUCTURE OF ALLUVIAL SEDIMENTS OF RIVER TERRACES AND ENERGY EFFICIENCY OF IRRIGATION SYSTEMS.....	89

<b>Y.M. Kalybekova, A.K. Zauirbek, I.S. Seitasanov, U.Q. Onglassyn*</b>	
INCREASING WATER PRODUCTIVITY IN IRRIGATION WITH REGARD TO GEOLOGY AND HYDROGEOLOGICAL CONDITIONS.....	101
<b>Z.S. Kenzhetayev, T.A. Kuandykov, K.S. Togizov, M.R. Abdraimova, M.A. Nurbekova</b>	
SELECTION OF RATIONAL PARAMETERS FOR OPENING AND DRILLING OF TECHNOLOGICAL WELLS UNDERGROUND URANIUM LEACHING.....	115
<b>R.A. Kozbagarov, K.K. Shalbayev, M.S. Zhiyenkozhayev, N.S. Kamzanov, G.T. Naimanova</b>	
DESIGN OF CUTTING ELEMENTS OF REUSABLE MOTOR GRADERS IN MINING.....	128
<b>T.A. Kuandykov, T.D. Karmanov, E.I. Kuldeyev, K.K. Yelemessov, B.Z. Kaliev</b>	
NEW TECHNOLOGY OF UNCOVER THE ORE HORIZON BY THE METHOD OF IN-SITU LEACHING FOR URANIUM MINING.....	142
<b>E. Orymbetov, G.E. Orymbetova, A.E. Khussanov, T.E. Orymbetov, B.E. Orymbetov</b>	
SECTIONING OF PETROLEUM GAS ADSORPTION DRYING.....	155
<b>A.M. Serikbayeva, M.S. Kalmakhanova, H.T. Gomes, B.B. Shagraeva, N.T. Shertaeva</b>	
METHODS OF PREPARATION AND PHYSICO-CHEMICAL CHARACTERISTICS OF ORGANIC MODIFIED CLAYS WITH GRAFTED ORGANOALOXIDES.....	166
<b>Zh. Zhantayev, D. Talgarbayeva, A. Kairanbayeva, D. Panyukova, K Turekulova</b>	
COMPLEX PROCESSING OF EARTH REMOTE SENSING DATA FOR PREDICTION OF LANDSLIDE PROCESSES ON ROADS IN MOUNTAIN AREA.....	181
<b>S.A. Istekova, A.K. Issagaliyeva, M.M. Aliakbar</b>	
BUILDING THE ONLINE GEOLOGICAL AND GEOPHYSICAL DATABASE MANAGEMENT SYSTEM FOR HYDROCARBON FIELDS IN KAZAKHSTAN.....	198

<b>R.E. Lukpanov, A.S. Yenkebayeva, D.V. Tsygulyov, Y.Y. Sabitov, D.S. Dyussembinov</b>	
ASSESSMENT OF ASH-STORAGE COOLECTOR STABILITY USING GEOSYNTHETIC REINFORCEMENT ELEMENTS BY TRAY TESTING AND NUMERICAL MODELING.....	212
 <b>T.K. Salikhov, D.K. Tulegenova, Zh.G. Berdenov, R.S. Sarsengaliyev, T.S. Salikhova</b>	
STUDY OF THE SOIL COVER OF ECOSYSTEMS OF THE CHINGIRLAUS DISTRICT OF THE WESTERN KAZAKHSTAN REGION ON THE BASIS OF THE APPLICATION OF GIS TECHNOLOGIES.....	226
 <b>A.R. Fazylova, G. Balbayev, B. Tultayev</b>	
SYSTEM OF SHORT-TERM FORECASTING OF WIND TURBINE OUTPUT POWER CONSUMPTION.....	243
 <b>O.G. Khaitov, A.A. Umirzokov, E.N. Yusupkhojaeva, S.P. Abdurakhmonova, N.G. Kholmatova</b>	
ASSESSMENT OF THE DENSITY OF THE WELL GRID IN THE SOUTHEASTERN PART OF THE BUKHARA-KHIVA REGION.....	253
 <b>K.T. Sherov, S.O. Tussupova, A.V. Mazdubay, M.R. Sikhimbayev, B.N. Absadykov</b>	
INCREASING DURABILITY OF THERMO-FRICTION TOOLS BY SURFACING.....	265

## **Publication Ethics and Publication Malpractice in the journals of the National Academy of Sciences of the Republic of Kazakhstan**

For information on Ethics in publishing and Ethical guidelines for journal publication see <http://www.elsevier.com/publishingethics> and <http://www.elsevier.com/journal-authors/ethics>.

Submission of an article to the National Academy of Sciences of the Republic of Kazakhstan implies that the described work has not been published previously (except in the form of an abstract or as part of a published lecture or academic thesis or as an electronic preprint, see <http://www.elsevier.com/postingpolicy>), that it is not under consideration for publication elsewhere, that its publication is approved by all authors and tacitly or explicitly by the responsible authorities where the work was carried out, and that, if accepted, it will not be published elsewhere in the same form, in English or in any other language, including electronically without the written consent of the copyright-holder. In particular, translations into English of papers already published in another language are not accepted.

No other forms of scientific misconduct are allowed, such as plagiarism, falsification, fraudulent data, incorrect interpretation of other works, incorrect citations, etc. The National Academy of Sciences of the Republic of Kazakhstan follows the Code of Conduct of the Committee on Publication Ethics (COPE), and follows the COPE Flowcharts for Resolving Cases of Suspected Misconduct ([http://publicationethics.org/files/u2/New\\_Code.pdf](http://publicationethics.org/files/u2/New_Code.pdf)). To verify originality, your article may be checked by the Cross Check originality detection service <http://www.elsevier.com/editors/plagdetect>.

The authors are obliged to participate in peer review process and be ready to provide corrections, clarifications, retractions and apologies when needed. All authors of a paper should have significantly contributed to the research.

The reviewers should provide objective judgments and should point out relevant published works which are not yet cited. Reviewed articles should be treated confidentially. The reviewers will be chosen in such a way that there is no conflict of interests with respect to the research, the authors and/or the research funders.

The editors have complete responsibility and authority to reject or accept a paper, and they will only accept a paper when reasonably certain. They will preserve anonymity of reviewers and promote publication of corrections, clarifications, retractions and apologies when needed. The acceptance of a paper automatically implies the copyright transfer to the National Academy of Sciences of the Republic of Kazakhstan.

The Editorial Board of the National Academy of Sciences of the Republic of Kazakhstan will monitor and safeguard publishing ethics.

Правила оформления статьи для публикации в журнале смотреть на сайтах:

[www.nauka-nanrk.kz](http://www.nauka-nanrk.kz)

<http://www.geolog-technical.kz/index.php/en/>

**ISSN 2518-170X (Online),**

**ISSN 2224-5278 (Print)**

Редакторы: *М.С. Ахметова, А. Ботанқызы, Р.Жәлиқызы, Д.С. Аленов*

Верстка на компьютере *Г.Д.Жадыранова*

Подписано в печать 15.06.2022.

Формат 70x90<sup>1/16</sup>. Бумага офсетная. Печать – ризограф.  
17,5 пл. Тираж 300. Заказ 3.